

Universitat de Lleida

Document downloaded from:

<http://hdl.handle.net/10459.1/64840>

The final publication is available at:

<https://doi.org/10.1016/j.solmat.2017.06.054>

Copyright

cc-by-nc-nd, (c) Elsevier, 2017



Està subjecte a una llicència de [Reconeixement-NoComercial-SenseObraDerivada 4.0 de Creative Commons](https://creativecommons.org/licenses/by-nc-nd/4.0/)

Considerations for the use of metal alloys as phase change materials for high temperature applications

A. Inés Fernández^{1,*}, Camila Barreneche¹, Martin Belusko², Mercè Segarra¹, Frank Bruno²,
Luisa F. Cabeza³

¹Materials Science & Engineering. Department of Materials Science & Physical Chemistry, Universitat de Barcelona, C/Martí i Franquès, 1-11, 08028, Spain

²Institute for Sustainable Systems and Technologies, University of South Australia, Mawson Lakes Boulevard, Mawson Lakes, SA 5095, Australia

³GREA Innovació Concurrent, Edifici CREA, Pere de Cabrera s/n, 25001, University of Lleida, Lleida, Spain

*Corresponding author: ana_inesfernandez@ub.edu

Abstract

The use of paraffin, salts and salt hydrates as phase change materials (PCMs) have been researched extensively and used in a number of commercial applications. However, metals and metal alloys, which possess a high storage density on a volume basis as well as a substantially higher thermal conductivity, has received much less attention. This paper discusses the considerations for the use of metal and metal alloys as phase change materials for high temperature thermal storage applications, as well as summarises the literature on the limited research in this area. Although some pure metals and metal alloys present interesting thermal properties to be used as PCMs in thermal storage systems, there is a lack of understanding on the implications of the metallurgical aspects related to the melting and solidification of these materials under thermal cycling at high temperatures. The main issues to be considered include vapour pressure, undercooling, corrosion, segregation, changes in composition and microstructure, changes in thermal properties and undesired reactions. Further research is needed before these materials can be used as PCMs in thermal energy storage systems in industry.

Key words: thermal energy storage (TES), phase change materials (PCM), metals, metal alloys, high temperature

1. Introduction

Climate change mitigation is one of the key issues to address for researchers and energy makers [1,2]. It is stated that there is an urgent need to develop a new energy supply system as sustainable as possible, that take into account our economic system and our social environment, with the aim of maintaining our resources for future generations. The widespread use of renewable energy has some handicaps, the most important being the intermittence of the resource. The mismatch between supply and demand can be overcome by storing the energy in the form of electricity, heat or mechanically.

Thermal energy storage (TES) is nowadays playing an important role as a complementary technology for renewable energy [3], enabling this energy resource to be utilised throughout the day and night. [4].

TES can use three methods to store heat: sensible heat (SHTES), latent heat (LHTES) and thermochemical storage (TCS) [5]. However, SHTES and LHTES using phase change materials (PCMs) have been more fully-developed and are more widespread in the market [6].

PCMs for high temperature TES systems are actually based on molten salts or eutectic salts compounds [7*]. However, metals can be a very important alternative, which researchers have started to explore [8].

In general, the required properties for a PCM to be used for heat storage can be summarized into three sets of requirements [9]: technical, economic and environmental. *Physical and technical requirements* determine the size and suitability of the thermal storage for a certain application. Low density variation and small volume change, high energy density, small or non-subcooling, non-phase segregation, low vapour temperature, chemical and physical stability, and compatibility with other materials are the most important properties to be considered when choosing a material within this group.

Thermophysical requirements are important for heat storage because the best thermal properties will support the greatest energy efficient system performance. A reproducible phase change at a temperature tailored to the application, with large phase change enthalpy (ΔH) and specific heat (C_p), as well as high thermal conductivity, and thermal and cycling stability, are the most relevant.

In addition, *economical requirements* are extremely significant, as a low price is a key issue to consider for a material for PCM implementation at large scale.

Last but not least, *environmental* concerns include the ability of the PCM to be recycled or reused, and other environmental factors such as the CO₂ footprint, which needs to be minimised, a low embodied energy, which is directly related to energy savings at the end of its life-cycle, or a low toxicity.

Although all of these requirements have their own importance for the development of TES technology using PCM, the improvement of thermophysical properties can provide new challenges as some of them are incompatible thus forcing to find a compromise between the most important ones.

The main objective of this paper is to assess the use of metal and metal alloys for TES, and to highlight which are the challenges of applying these types of materials from the materials science point of view.

2. State of the art on use of metal and metal alloys as TES materials media.

Gasanaliev and Gamataeva [10] analyse the thermophysical properties of various thermal cycles and have also specified the perspectives of using metal alloys for heat accumulation. A technical and economic analysis showed that accumulators with high-temperature phase-transition (melting point > 500 °C) as heat-carriers, particularly eutectic compositions of salt and metal multi-component systems, are most suitable for non-traditional energy sources [11].

Of all the PCMs used for thermal energy storage, eutectic metal alloys have the greatest thermal conductivities and best stabilities. The analysis of published data on thermodynamic parameters of metal-based multi-component systems [12,13] has made it possible to single out the most promising ones to be used as working materials in heat accumulators (Table 1).

Sharma et al. (2009) [14], Liu et al. (2012) [7] and Rathod and Banerjee (2013) [15] considered some metals and metal eutectics with low melting temperatures as high temperature PCM. The authors claim that these metals have not yet been seriously considered for PCM technology because of weight penalties. However, when volume is taken into account, they become good candidates due to their high heat of fusion per unit volume. Metals and metal alloys also have high thermal conductivities, so fillers normally added in PCM (with added weight penalties) are not required.

A list of some selected metals and alloys is presented in Table 1. Some of the features of these materials are common to all: (i) low heat of fusion per unit weight, (ii) high heat of fusion per unit volume, (iii) high thermal conductivity, (iv) low specific heat, and (v) relatively low vapour pressure.

Birchenall and Telkes [16], and later Kenisarin (2010) [17], were the first authors who analysed the possibility of storing thermal energy by using the heat of fusion of metals. Starting from that work, Birchenall and Riechman [18] have studied some metal eutectic alloys. Thermal properties of alloys were determined by a differential-scanning calorimeter (DSC) and differential-thermal analysis (DTA). The compositions of the selected alloys were taken from the literature. Initial metals were alloyed in a graphite crucible. The eutectic composition was proved by optical metallography. Experimental facilities were preliminary calibrated by means of pure metals. The measurement error of DTA was 4% for heat of fusion, and 3 K for melting temperature. For DSC, the measurement error was 2% and 1 K, respectively. Five years later, Farkas and Birchenall [19] published new results of the determination of thermophysical properties of some new alloys.

Wang et al. [20] developed and investigated two compositions based on aluminium and silicon. The first alloy, AlSi₁₂, contained 12 wt.% silicon, and the second alloy, AlSi₂₀, 20 wt.% silicon. AlSi₁₂ had a melting temperature of 576 °C and a heat of fusion of 560 J/g, and AlSi₂₀ 585 °C and 460 J/g, respectively. Owing to the best properties, alloy AlSi₁₂ was chosen for further studies (its thermophysical properties are given in Table 1). This alloy was used to develop and test a high-temperature isothermal electric heater intended as thermal energy storage at night, when the tariff for the electric power is essentially lower.

Sun et al. [21] investigated one of the ternary eutectic alloys based on aluminium, listed by Farkas and Birchenall 16, Al (60 wt.%)–34Mg–6Zn. In this study, the compatibility of the specified alloy with materials such as stainless steel SS304L and carbon steel C20 was investigated. The variation in thermal properties of the alloy in regards to the number of melting and solidification thermal cycles was also studied.

Table 1. Metals and metal alloys considered in the literature as PCMs for high temperature applications.

Material	Melting point (°C)	Latent heat		Density (kg/L)	Cp (sol) (kJ/kg·K)	Cp (liq) (kJ/kg·K)	Thermal conductivity (W/m·K)	Volume expansion (10 ⁻⁶ /K)	Type	Reference
		(kJ/kg)	(kJ/L)							
52Zn-48Mg	340	180	---	---	---	---	---	---	---	[10,19,23]
53.7Zn-46.3Mg	340	185	851	4.600	---	---	---	---	Eutectic	[10,22-24]
51Zn-49Mg	342	155	442	2.850	0.73	---	75	---	Eutectic ⁽¹⁾	[25]
96Zn-4Al	381	138	916	6.630	---	---	---	---	Eutectic	[[10,23-24]
55Mg-28-17Zn	400	146	---	2.26	---	---	---	---	---	[19]
Zn (com purity, min 99.9%)	419	112	---	7.140	0.39	0.48	---	93.5****	---]	[26]
59Al-35Mg-6Zn*	443	310	---	2.38	1.63	1.46	---	---	---	[10,19,23]
60Al-34Mg-6Zn	443	312	---	2.380	1.63	1.46	---	80.1-93.5	---	[26]
60Al:34Mg:6Zn	450.3	32.1	---	---	---	---	---	---	---	[23,27]
60Mg-25Cu-15Zn	452	254	---	2.80	---	---	---	---	---	[10,19,23]
52Mg-25Cu-23Ca	453	184	---	2.00	---	---	---	---	---	[10,19,23]
86.4Al-9.4Si-4.2Sb	471	471	---	---	---	---	---	---	Eutectic	[23-24]
34.65Mg-65.35Al	497	285	615	2.155	---	---	---	---	Eutectic	[10,23-24]
60.8Al-33.2Cu-6.0Mg	506	365	111.3	3.050	---	---	---	---	Eutectic	[10,23-24]
64.1Al-5.2Si-28Cu-2.2Mg	507	374	164.4	4.400	---	---	---	---	Eutectic	[10,23-24]
54Al-22Cu-18Mg-6Zn	520	305	---	3.14	1.51	1.13	---	---	---	[10,19,23]
68.5Al-26.5Cu-5.0Si	525	364	106.9	2.938	---	---	---	---	Eutectic	[10,23-24]
64.3Al-34.0Cu-1.7Sb	545	331	132.4	4.000	---	---	---	---	Eutectic	[10,23-24]
66.92Al-33.08Cu	548	372	133.9	3.600	---	---	---	---	Eutectic	[10,23-24]
83.14Al-11.7Si-5.16Mg	555	485	121.3	2.500	---	---	---	---	Eutectic	[10,23-24]
87.76Al-12.24Si	557	498	126.5	2.540	---	---	---	---	Eutectic	[10,23-24]
49.1Cu-46.3Al-4.6Si	571	406	226.0	5.560	---	---	---	---	Eutectic	[10,23-24]
65Al-30Cu-5Si	571	422	---	2.73	1.30	1.20	---	---	---	[10,19,23]
86.4Al-9.4Si-4.2Sb	575	471	127.2	2.70	---	---	---	---	Eutectic	[10,23-24]
88Al-12Si	576	560	---	2.70	1.038	1.741	160	---	Alloy	[20]
88Al-12Si	576	560	---	2.700	1.04	1.74	---	63.9**	Metal	[26]
86Si:12Al	576	560	---	2.700	---	---	---	---	Metal	[23,21]
88Al-12Si	576	560	---	---	---	---	---	---	Alloy	[28-30]
88Al-12Si	577	462	---	---	0.939	---	181	---	Alloy	[28,31-32]
80Si:20Al	585	460	---	---	---	---	---	---	Alloy	[21,23]

Table 1. (following part)

Zn ₂ Mg	588	230	---	---	---	---	---	---	---	[19]
Mg (commercial purity)	648	365	---	1.740	1.27	1.37	---	87**	Metal	[26]
Al (commercial purity, 1-0 wrought)	661	388	---	2.700	0.90	0.90	---	80.1***	Metal	[26]
49Zn-45Cu-6Mg	703	176	---	8.67	0.42	---	---	---	Alloy	[10,19,23]
91Cu-9P	715	134	---	5.60	---	---	---	---	Alloy	[10,19,23]
69Cu-17Zn-14P	720	368	---	7.00	---	---	---	---	Alloy	[9,10,19,23,27,29] ,29
74Cu-19Zn-7Si	765	125	---	7.17	---	---	---	---	Alloy	[10,19,23]
56Cu-27Si-17Mg	770	420	---	4.15	0.75	---	---	---	Alloy	[10,19,23]
84Mg-16Ca	790	272	---	1.38	---	---	---	---	Alloy	[10,19,23]
47Mg-38Si-15Zn	800	314	---	---	---	---	---	---	Alloy	[10,19,23]
80Cu-20Si	803	197	---	6.60	0.50	---	---	---	Alloy	[10,19,23]
83Cu-10P-7Si	840	92	---	6.88	---	---	---	---	Alloy	[10,19,23]
Mg ₂ Cu	841	243	---	---	---	---	---	---	Alloy	[19]
49Si-30Mg-21Ca	865	305	---	2.25	---	---	---	---	Alloy	[10,19,23]
56Si-44Mg	946	757	---	1.90	0.79	---	---	---	Alloy	[10,19,23]
Cu	1077	71	---	---	---	---	---	---	Metal	[33-34]

1 The metal samples investigated were immersed in a capsule, which were placed in a stainless
 2 steel crucible. The crucible with samples underwent 1000 thermal cycles between 442 and 455
 3 °C. The duration of one melting and solidification cycle was 34 min. The measurement of
 4 thermal properties was conducted using a DSC. The change of melting temperature of the alloy
 5 is presented in Table 2. Note that controlling the cooling rates may improve the phase formation
 6 stability. Thereby, a considerable change in melting temperature of the alloy was not observed.
 7 On the other hand, the heat of fusion tends to decrease as the number of cycles increase: -0.13%
 8 after 50 cycles -7.46% after 500 cycles and -10.98%. The reason of this decrease has not been
 9 established, but it could be explained as a microstructure change as stated by Feng Li et al. [29].

11 **Table 2. Change of melting temperature of the Al(59)-35Mg-6Zn alloy 25**

	0 cycles	50 cycles	500 cycles	1000 cycles
Melting temperature (°C)	450.3-455.7	450.3-454.3	448.6-452.8	447.3-450.4

12
 13 Khare et al. (2012) [26] used a materials selection procedure and found that metals such as Al,
 14 Mg, Si and Zn, and their eutectics 88Al-12Si and 60Al-34Mg-6Zn were highly suitable as a
 15 PCM for the duty considered in their research (steam generation from 400 to 750 °C). Their
 16 properties, heat of fusion, thermal conductivity, etc. have advantages in the application
 17 considered over traditional molten salts, with 88Al-12Si showing the best environmental
 18 performance as well. The heat transfer effectiveness of this alloy was also evaluated by the e-
 19 NTU method [26] and favourably compared to the HiTech nitrate based molten salt using heat
 20 exchanger geometry. The authors used materials selection software based on a multi-objective
 21 optimisation methodology, by considering environmental conditions and eco-properties.

22
 23 Sun et al. [4, 21] determined the thermal stability and corrosion characteristics of Al-34%Mg-
 24 6%Zn alloy when used as latent heat energy storage material. The melting temperature and
 25 latent heat of fusion for this alloy were 454 °C and 314.4 J/g, respectively. Thermal stability was
 26 checked for 1000 thermal cycles, but the microstructure potential changes were not taken into
 27 account. The container materials considered in the corrosion tests carried out in this study were
 28 stainless steel (SS304L) and carbon steel (SteelC20). The DSC results indicated that the change
 29 of the melting temperature of the alloy was in the range of 3.06–5.3 °C, and that the latent heat
 30 of fusion decreased 10.98% after 1000 thermal cycles. The results showed that the Al-34%Mg-
 31 6%Zn alloy under study had reasonably good thermal reliability as a latent heat energy storage
 32 material. Table 1 shows the details of the above-mentioned material.

33
 34 Cárdenas and León (2013) [23] listed the metals and metal alloys with melting temperatures
 35 above 300 °C proposed and studied by various other researchers as possible high temperature

12 PCM. As previous authors, they claimed that the use of metal alloys as a PCM had been
 13 underestimated by researchers even though they have desirable properties such as high thermal
 14 conductivity, high corrosion resistance, and small volume change associated with phase change,
 15 and no subcooling. Therefore, for certain applications, metal and metal alloys present higher
 16 thermophysical properties and they are able to compete with salts, especially when weight is not
 17 a decisive factor. Nieto-Maestre et al [35] focused in the particular temperature range between
 18 285°C and 330°C for direct steam generation DSG, using Thermo-Calc software and SSOL4
 19 thermodynamic database for different ternary and quaternary metallic systems combining Mg
 20 and Zn, with Cu and Ni for the ternary systems and Mg-Zn-Al-Cu, Mg-Zn-Al-Sn, Mg-Zn-Cu-
 21 Sn, for the quaternaries, though the most promising eutectics in terms of T_m and ΔH_f were the
 22 ternary combinations.

13

16 In addition, some authors propose that the use of eutectic metals as TES medium is feasible for
 17 industrial processes [18], that metals and metal alloys can be used as waste heat storage media
 18 [36], and that AlSi₁₂ [20] and AlMg₃₄An₆ [21] are also suitable to be used as PCM.

17

18 Pure metals as PCM

21 PCM store energy following the Eq. 1 where Q_{latent} is the heat accumulated during the phase
 22 change as latent heat, C_p is the specific heat at solid ($C_{p,s}$) or liquid ($C_{p,l}$) stage and ΔH_{pc} is the
 23 phase change enthalpy.


22

$$Q_{latent} = \int_{T_1}^{T_{pc}} C_{p,s} \cdot dT + \Delta H_{pc} + \int_{T_{pc}}^{T_2} C_{p,l} \cdot dT \quad (1)$$

23

35 Zhang et al. (2014) [33] used copper as PCM and encapsulated it with refractory metallic shells,
 36 to be used up to 1000 °C. Copper spheres with a diameter of few millimetres were encapsulated
 37 with a thick chromium–nickel bilayer by a novel chromium periodic-barrel electroplating
 38 method and a nickel barrel-plating method. The latent heat density of as-prepared capsules was
 39 up to 75% of the theoretical value (about 71 J/g) at the melting temperature of 1077 °C, and the
 40 thermal resistance of chromium–nickel layer was $8.27 \cdot 10^{-6} \text{ m}^2 \cdot \text{K/W}$. Principally, copper
 41 capsules could endure 1000 charge–discharge thermal cycles from 1050 °C to 1150 °C without
 42 any leakage. The structure investigations (see Figure 1) revealed the excellent oxidation
 43 resistance of the capsules and good stability between copper and the chromium–nickel layer,
 44 even after long-term charge–discharge cycles. The results demonstrated that as-prepared copper
 45 capsules were applicable as high temperature PCM, which could facilitate high temperature
 46 thermal energy storage systems.

36

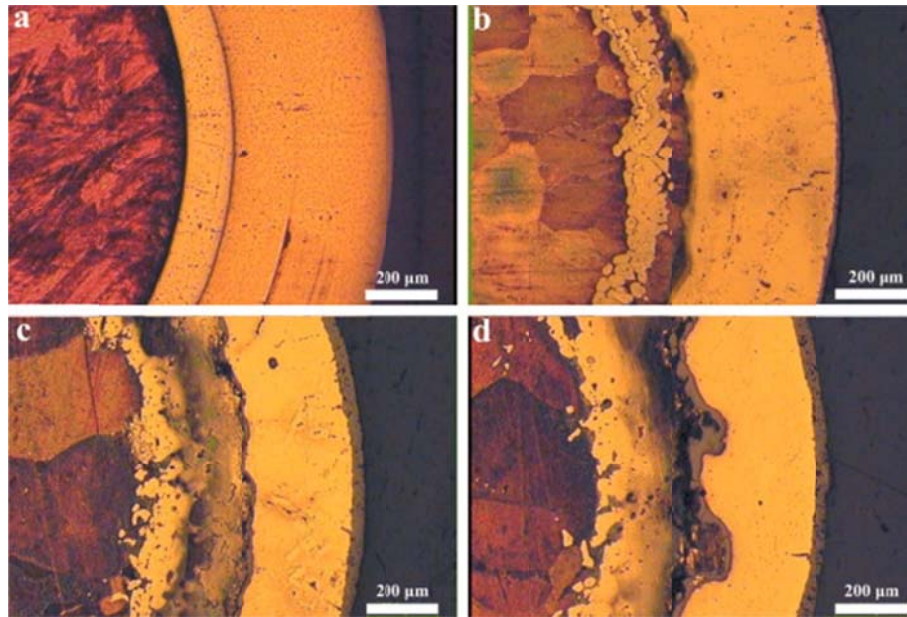

2
4 **Figure 1. Morphology change of capsules with different charge–discharge cycles from 1050 °C to**
5 **1150 °C [33]**

5
12 Ma et al. (2014) [31] used copper as PCM and encapsulated it with iron at micro level. They
13 discussed the formation of Fe-Cu alloys. Results showed that the morphology evolution of Fe–
14 Cu alloys could be attributed to the combined effects of the liquid phase fraction of the two
15 immiscible liquids, Stokes and Marangoni velocities of droplets, and the rotation direction of
16 the alloy samples during solidification. This type of encapsulated metallic-PCM (EM-PCM) is
17 nearly spherical with a diameter of about 2 mm and coated by an iron oxide layer which can
18 improve the wear resistance of EM-PCMs.

13
14 Metal alloys as PCM

24 Kotzé et al. (2013) [28] selected the eutectic alloy of aluminium and silicon, AlSi₁₂, as one of
25 the best candidates as metallic PCM based on a review of the literature. This alloy has a heat of
26 fusion of 560 J/g and a melting point of 576 °C [20]. Li et al. [29] conducted a study on the
27 suitability of aluminium–silicon alloys when used as PCM. They found that aluminium–silicon
28 alloys are relatively stable through multiple heating and cooling cycles. In addition, Kotze et al.
29 (2014) [32] used the same eutectic aluminium silicon alloy (AlSi₁₂) as PCM in a prototype
30 thermal energy storage test rig because of its moderate melting temperature, high thermal
31 conductivity, and high heat of fusion. The concept is shown in Figure 2. Note that the PCM is
32 located inside tubes and the steam cross these tubes by water pipes (with dots) in combination
33 with NaK pipes (black dots).

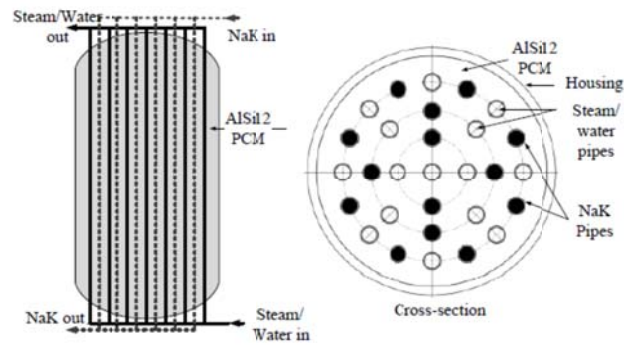


Figure 2. Kotze et al. concept composed by AlSi₁₂ [32].

2
3
4

11 Blanco-Rodríguez et al. (2014) [25] presented a eutectic metal alloy, Mg-51%Zn, to be used as
 12 PCM for TES in CSP. They characterized extensively this eutectic metal alloy between room
 13 temperature and its melting temperature according to the phase diagram. A first conclusion
 14 drawn by these authors is that the phases present at room temperature depend on the synthesis
 15 settings and subsequent heating and cooling cycles. On the one hand, the main advantages of
 16 this eutectic metal alloy are its better thermal diffusivity, heat capacity and energy density
 17 compared to molten salts. On the other hand, the main drawback is its price.

14 Moreover, Risueño et al. [37] have developed some light-weight alloys based on Mg-Zn-Al to
 15 be used in latent heat storage applications. They suggest that among the studied compositions,
 16 the Mg₇₀Zn_{24.9}Al_{5.1} eutectic alloy could be the best candidate.

18 Andraka et al. [35], have synthesized and characterized metallic based PCM composed by CaSi
 19 (T_m 782 °C) and CuMgSi (T_m 742 °C), as proposed storage system for matching the
 20 isothermal input feature of Stirling engines. Their study includes evaluation of compatibility
 21 with container materials, and center the compatibility issues on silicon.

20 These very recent publications put on relevance the potential of these kind of materials as well
 21 as these thermal conductivity properties, phase change issues, energy density, etc.

21
22

23 3. Melting/solidification of pure metals and metal alloys

24

28 Usually, a pure metal solidifies by crystallization through nucleation and crystal growth, leading
 29 to a polycrystalline structure. It occurs in some of the three common crystal structures: body-
 30 centred cubic or BCC (Na, K, Mo, Fe, Ti), face-centred cubic or FCC (Al, Co, Cu, Fe), and
 31 hexagonal close-packed or HCP (Cd, Co, Mg, Ti, Zn), showing some of them polymorphism.

29

31 There are two types of nucleation: homogeneous and heterogeneous. In the first one, new phase
 32 nuclei appear in all the bulk material, while in the second, the first nuclei are formed just next to

1 any heterogeneity present in the material, such as solid impurities or grain boundaries, or even
2 at the container walls.

3

4 Assuming homogeneous nucleation, and knowing the interfacial energy, γ , between a crystal
5 and its melt, the degree of subcooling is estimated as $\theta \cong 0.2T_m$ [38]. After nucleation, crystal
6 growth occurs at a rate that increases as the square of the degree of subcooling, giving very fast
7 rates in pure metals, e.g. 40 m/s in Ni undercooled 175°C [38]. In foundries, the temperature of
8 interface is near the ideal melting point and thus the rate of growth becomes the rate of removal
9 of latent heat from the interface.

10

11 As stated by Professor Cottrell [38], the presence of impurities may lead to changes of viscosity
12 entailing to pre-crystallization before reaching the thermodynamic transition temperature, and
13 thus affecting the freezing behaviour. Otherwise, a dendritic growth occurs in cast impure
14 metals because the soluble impurities and alloying elements promote dendritic crystallisation,
15 thus revealing microstructures with inhomogeneous composition, having, as a consequence,
16 constitutional undercooling. Casted metals may show different structures because of the
17 selective growth forming grains with different sizes or shapes: columnar or equi-axed.
18 Moreover, by modifying the temperature gradient starting from a superheated liquid, or
19 increasing the cooling rate, may lead to extremely different structures with a coarse columnar
20 structure for the first case, and a fine grained equi-axed crystals structure for the second one.

21

22 Moreover, other factors influencing the grain structure and determining the quality of a cast
23 metal are shrinkage, segregation and gas evolution. Shrinkage originates many practical
24 difficulties in the casting of metals as it produces mechanical stresses and cracks, e.g.
25 aluminium shrinks about 12% in volume from the liquid to the solid state at room temperature.
26 It is important at microscopic scale as it can lead to a casting full of fine-scale porosity.
27 Segregation refers to all non-uniformities of composition in an ingot or casting, and can be
28 macro- or micro-segregation. When melted, metals can dissolve gases in some extent,
29 independently on the gases present during the solidification process (oxygen, nitrogen, argon,
30 etc.).

31 , and the presence of gas during solidification has different effects: it can react with the metal,
32 form gas bubbles or even thin cracks yielding to brittle metals. Degassing is a crucial step
33 during casting and it can be done by direct removal or using vacuum in different furnace
34 configurations.

35

36 To predict the phase change in an alloy, the phase diagram and the lever rule are used to state
37 the phases present, and their relative amounts and composition at a given temperature. To do so,

1 it is assumed that the alloy remains in equilibrium throughout all the solidification/melting
2 process, and that it is possible only if the change in temperature is slow enough to allow
3 diffusion and nucleation to occur. The production of metal alloys focuses on obtaining the
4 desired microstructures with specific properties, and for this purpose, the whole process is
5 designed: melting, cooling and further heat treatment.

6 7 **4. Challenges of using metal and metal alloys as storage materials, and how to approach** 8 **them.**

9
10 a. As discussed previously, the use of pure metals in TES high temperature applications is a
11 promising solution. Nevertheless, some pure metals have quite a high vapour pressure, e.g.
12 Mg, Zn, Hg, Na that make them non-suitable to be as PCM. Selection of metals and alloys
13 with low vapour pressures becomes crucial. Steel, copper and copper alloys without Mg, Zn
14 or Na are examples of PCM taking into account vapour pressure [38].

15
16 b. In pure metals, undercooling will occur either with homogeneous or heterogeneous
17 nucleation. While this phenomenon is not crucial in industrial casting, it definitely must be
18 taken into account in a TES system. For both Mg and Al, undercooling is estimated to be
19 above 100 K for homogeneous nucleation [38]. This data should be collected while
20 considering a certain metal or alloy a suitable PCM.

21
22 c. Most of metal alloys suggested for TES storage up to now are compositions close to the
23 eutectic point of these alloys. The design of a storage process with implications in the
24 microstructure, by forming metastable phases, precipitates, etc. was remarked by Chen et al.
25 [39]. To maintain the phase-change transformation closer to the thermodynamic equilibrium
26 conditions, the melting/solidification process should be as slow as possible. This will also
27 favor the absence of thermal stresses in the bulk material when the cooling or heating front
28 propagates inwards from the surface by diffusion. This can be translated to a lower
29 diffusivity for the material. In order to maintain the phase-change transformation closer to
30 the thermodynamic equilibrium conditions, the melting/solidification process should be as
31 slow as possible.

32
33 The time t that heat takes to go through a thickness x in a material with diffusivity a , is:

$$t = \frac{x^2}{2a}$$

1 So, in order to increase time, the diffusivity should be as low as possible [40-41]. As
2 diffusivity is the relation between conductivity (λ) and volumetric heat capacity ($\rho \cdot C_p$), the
3 equation is as follows:

$$t = \frac{x^2 \rho C_p}{2 \lambda} \quad (2)$$

5
6 Therefore, to increase lag time, we have to find metals or alloys with a relation $\frac{\rho C_p}{\lambda}$ as large
7 as possible, or the inverse minimum. On the other hand, the metal or metal alloy, need to
8 store a large amount of heat for a certain temperature ranges. Stored heat per unit volume
9 can be calculated by (Eq. 3):

$$Q_{stored} = \rho C_p \Delta T \quad (3)$$

11
12 So, $\rho \cdot C_p$ must be as high as possible. The heat transferred through the material depends on
13 its thermal conductivity, transferred heat per unit volume become Eq. 4:

$$Q_{transferred} = \lambda \frac{\Delta T}{x^2} \quad (4)$$

15
16 Thus, $\rho \cdot C_p$ should also be as large as possible. Following the material selection
17 methodology described by Fernández et al. [40], if all these requirements are considered
18 minimum, those metals or alloys with the lower diffusivity can be found but, at the same
19 time, the highest thermal conductivity and volumetric heat capacity (see Figure 3).

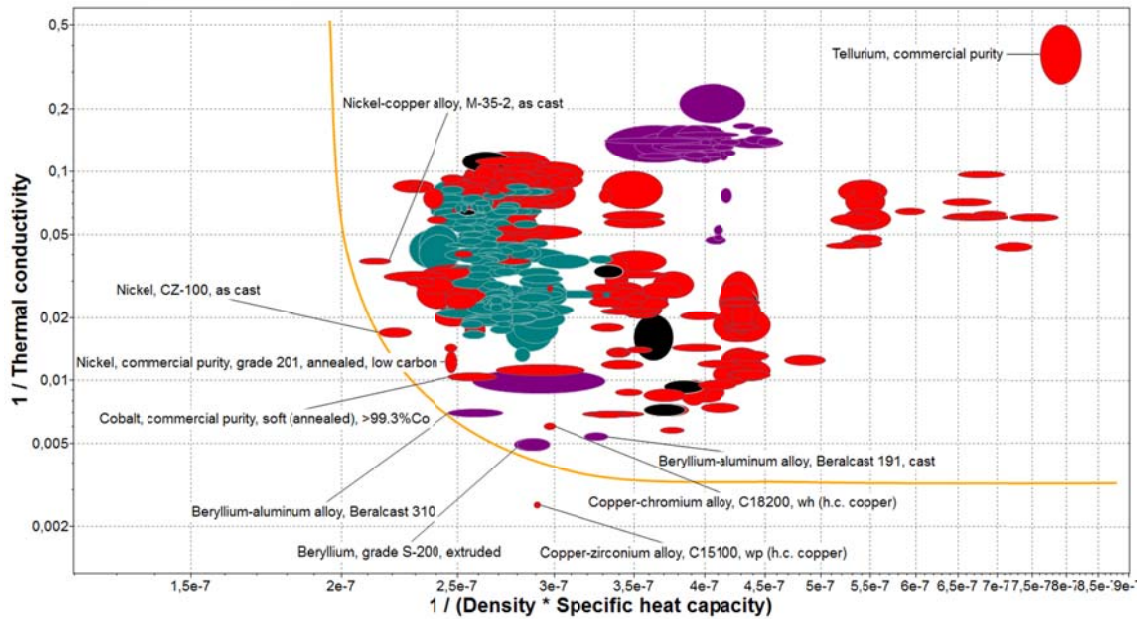


Figure 3. Thermal conductivity vs. $\rho \cdot Cp$


Those materials that are closer to the Pareto front (curved line) present lower diffusivities, while the other properties are greater [40-41].

- d. The heat transfer coefficient is very high in metal alloys. Hence, to use or choose a proper heat transfer fluid that allows working with these high heat transfer coefficients is a challenge in this field. Another important issue is the difference in expansion coefficients between the PCM and the container material. This should be reduced as much as possible in order to diminish thermal stresses [41].
- e. In practice, most metal alloys require a heat treatment after the solidification to reach the desired microstructure that provides the required mechanical and chemical properties of these alloys in use. If this mechanical performance is not required, then this heat treatment can be excluded, but then the different heating and cooling cycles in their use as PCM may produce segregation or formation of insoluble precipitates. The effect of the number of heating/cooling cycles on the microstructure becomes an important parameter to be studied.
- f. The formation of precipitates or oxides due to the change in cycling rates (which may be a requirement of the storage system) may change the alloy characteristics, and therefore melting and solidification temperatures as well as the enthalpy. Therefore, precipitates must be included in the boundary conditions in order to define the working condition limits.
- g. Oxidation of alloys can be avoided with inert atmospheres, but each gas has a different influence that needs to be considered in the final solid phase formation. The effect of gases

1 on molten metals has already been studied in the past, but the influence of retained gases in
2 the solid metal or alloy during cycling needs a further research.

3
4 h. Encapsulation or containment represents a significant challenge, which is difficult to
5 achieve cost effectively. A metal PCM can either be contained by a ceramic or a metal.
6 With a ceramic, the differences in thermal expansion can expose the ceramic to significant
7 strain, ultimately causing fracture. A metal containment/encapsulation can resolve this
8 issue; however, there is a significant risk of corrosion through diffusion. Through this
9 process intermetallic may form. Various oxide coatings could potentially overcome this
10 issue.

11
12 i. Possible undesired reactions with the container, coil, pipes and liquid metal can take place⁴⁰.
13 Considerations within the system design step shall include the inquiry of the Ellingham
14 diagrams. For instance, the use of refractory materials, which is common in the various
15 types of industrial furnaces, shows an example of undesirable reactions between a magnesia
16 brick and liquid aluminium following the reaction:



17
18
19
20 On the other hand, experience from the metallurgical industry may help in the materials
21 selection of the system, e.g. tool steel is used for die casting of Al and Al alloys.
22 Compatibility of PCM and container materials should be tested.

23 j. Last but not least, the solidification during the phase change will be one of the most
24 important processes to store thermal energy with metal and/or metal alloys. In practice, the
25 speed of crystallization of a substance under solidification is defined by crystal structure,
26 presence of crystallization centers, external conditions of heat exchange, etc as state by
27 Kenisarin [17]. Moreover, high changes of volume during the melting and this fact can
28 promote formation of voids during its solidification.

30 **5. Conclusions and recommendations**

31
32 Although some pure metals and metal alloys present interesting thermal properties to be used as
33 PCMs in thermal storage systems, there is still a lack of consciousness about the implications of
34 the metallurgical aspects related to melting and solidification of these materials under thermal
35 cycling at high temperatures.

1 The main issues to be considered have been summarized in this paper: vapour pressure,
2 undercooling, corrosion, segregation, changes in composition and microstructure, changes in
3 thermal properties, and undesired reactions. All of them seem to be sufficiently important by
4 themselves, but significantly more research is needed before implementing these materials as
5 PCMs in TES at industrial scale.

6

7 **Acknowledgments**

8

9 The research leading to these results has received funding from the European Commission
10 Seventh Framework Programme (FP/2007-2013) under grant agreement n° PIRSES-GA-2013-
11 610692 (INNOSTORAGE) and from the European Union's Horizon 2020 research and
12 innovation program under grant agreement No 657466 (INPATH-TES). The authors would like
13 to thank the Catalan Government for the quality accreditation given to their research groups
14 GREA (2014 SGR 123) and DIOPMA (2014 SGR 1543), and also the Spanish Government for
15 the projects ENE2015-64117-C5-1-R and ENE2015-64117-C5-2-R (MINECO/FEDER, UE).
16 Dr. Camila Barreneche would like to thank Ministerio de Economía y Competitividad de
17 España for Grant Juan de la Cierva, FJCI-2014-22886. This paper was produced with support
18 from the "Premier's Research and Industry Fund - International Research Grant Program",
19 funded by the government of South Australia.

20

21 **References**

- 22 1. Lucon, O., Ürge-Vorsatz, D., Zain Ahmed, A., Akbari, H., Bertoldi, P., Cabeza, L.F.,
23 Eyre, N., Gadgil, L.D.D., Harvey, A., Jiang, Y., Liphoto, E., Mirasgedis, S., Murakami,
24 S., Parikh, J., Pyke, C., Vilariño, M.V. Buildings. In: Climate Change 2014: Mitigation of
25 climate change. Contribution of working group III to the fifth assessment report of the
26 intergovernmental panel on climate change [Edenhofer, O., Pichs-Madruga, R., Sokona,
27 Y., Farahani, E., Kadner, S., Seyboth, K., Adler, A., Baum, I., Brunner, S., Eickemeier,
28 P., Kriemann, B., Savolainen, J., Schlömer, S., von Stechow, C., Zwickel, T., Minx, J.C.
29 (eds.)]. Cambridge University Press, Cambridge, United Kingdom and New York, NY,
30 USA. 2014
- 31 2. Ürge-Vorsatz, D., Cabeza, L.F., Serrano, S., Barreneche, C., Petrichenko, K. Heating and
32 cooling energy trends and drivers in buildings. *Renewable & Sustainable Energy Reviews*
33 41, 85-98. 2015.
- 34 3. Cabeza, L.F., Martorell, I., Miró, L., Fernández, A.I., Barreneche, C. Introduction to
35 thermal energy storage (TES) systems. *Advances in Thermal Energy Storage Systems:
36 Methods and Applications* 1-28. 2014.

- 1 4. Gil, A., Medrano, M., Martorell, I., Lázaro, A., Dolado, P., Zalba, B., Cabeza, L.F. State
2 of the art on high temperature thermal energy storage for power generation. Part 1-
3 Concepts, materials and modellization. *Renewable & Sustainable Energy Reviews* 141,
4 31-55, 2010.
- 5 5. Cabeza, L.F., Galindo, E., Prieto, C., Barreneche, C., Inés Fernández, A. Key
6 performance indicators in thermal energy storage: Survey and assessment. *Renewable*
7 *Energy* 83, 820-827, 2015.
- 8 6. Cabeza, L.F., Castell, A., Barreneche, C., De Gracia, A., Fernández, A.I. Materials used
9 as PCM in thermal energy storage in buildings: A review. *Renewable and Sustainable*
10 *Energy Reviews* 15 (3), 1675-1695, 2011.
- 11 7. Liu M, Saman W and Bruno, F. Review on storage materials and thermal performance
12 enhancement techniques for high temperature phase change thermal storage systems.
13 *Renewable and Sustainable Energy Reviews* 16, 2118– 2132, 2012.
- 14 8. Francis Agyenim, Neil Hewitt, Philip Eames, Mervyn Smyth. A review of materials, heat
15 transfer and phase change problem formulation for latent heat thermal energy storage
16 systems (LHTESS). *Renewable and Sustainable Energy Reviews* 14, 615–628, 2010.
- 17 9. Barreneche, C. et.al Thermal Energy Storage (TES): Requirements and constrains for a
18 material-based design. *Materials Science and Technology Conference and Exhibition*
19 2014, MS&T2014, 3,1651-1658, 2014.
- 20 10. Gasanaliyev, A.M, Gamataeva, B.Y. Heat-accumulating properties of melts. *Russian*
21 *Chemical Reviews* 69(2),179–186, 2000.
- 22 11. Magomedov A.M. *Netraditsionnye Istochniki Energii (Non-Traditional Sources of*
23 *Energy. Makhachkala: Yupiter, 1996*
- 24 12. Martynova, N.M., Rodionova, E.K., Tishura, T.A., Cherneeva, L.I. *Akkumulirovanie*
25 *Energii i Puti, Povysheniya Effektivnosti Raboty Elektrostantsii i Ekonomii Energii.*
26 *Akkumuliruyushchie Energoustanovki, Teplovye Protsessy i Teploakkumuliruyushchie*
27 *Materialy (Energy Storage and Ways of Increasing the Efficiency of Operation of Power*
28 *Plants and Economy of Energy). Stored Power Plants, Thermal Processes and Heat-*
29 *Storage Materials. Moscow: Khimiya, 2, 167, 1986.*
- 30 13. Danilin, V.N., Shurai, P.E., Sryvalin, I.T., Krasnodar, Tr. Politekh. In-ta 65, 1969.
- 31 14. Sharma, A., Tyagi, V.V., Chen, C.R., Buddhi, D. Review on thermal energy storage with
32 phase change materials and applications. *Renewable and Sustainable Energy Reviews* 13,
33 318–345, 2009.
- 34 15. Rathod, M.K., Barnerjee, J. Thermal stability of phase change materials used in latent
35 heat energy storage systems: A review. *Renewable & Sustainable Energy Reviews* 18,
36 246–258, 2013.

- 1 16. Birchenall, C.E., Telkes, M. Thermal storage in metal. In: Sharing the sun: solar
2 technology in the seventies-joint conf. American section of ISES and solar energy society
3 of Canada 8, 38-54, 1976.
- 4 17. Kenisarin, M.M. High-temperature phase change materials for thermal energy storage.
5 Renewable and Sustainable Energy Reviews 14, 955–970, 2010.
- 6 18. Birchenall, C.E., Riechman, A.F. Heat storage in eutectic alloys. Metallurgical
7 Transactions A 11A (8), 1415–1420, 1980.
- 8 19. Farkas D., Birchenall C.E. New eutectic alloys and their heats of transformation.
9 Metallurgical Transaction A16A,324–328, 1985.
- 10 20. Wang, X., Liu, J., Zhang, Y., Di, H., and Jiang, Y. Experimental Research on a Kind of
11 Novel High Temperature Phase Change Storage Heater. Energy Conversion and
12 Management 47, 2211–2222, 2006.
- 13 21. Sun JQ, Zhang RY, Liu ZP, Lu GH. Thermal reliability test of Al-34% Mg-6%Zn alloy
14 as latent heat storage material and corrosion of metal with respect to thermal cycling.
15 Energy Convers Manage 48,617–624, 2007.
- 16 22. Gunasekara S.N., Martin V., Chiu J.N. Phase equilibrium in the design of phase change
17 materials for thermal energy storage: State-of-the-art. Renewable and Sustainable Energy
18 Reviews 73, 558–581, 2017.
- 19 23. Cárdenas, B., León, N. High temperature latent heat thermal energy storage: Phase
20 change materials, design considerations and performance enhancement techniques.
21 Renewable & Sustainable Energy Reviews 27, 724–737, 2013.
- 22 24. Trunin, A.S. Designing and investigations of salt systems for solar energy utilization.
23 Utilization of sun and other radiation sources in materials research. Kiev: Naukova
24 Dumka 228–238, 1983.
- 25 25. Blanco-Rodríguez, P., Rodríguez-Aseguinolaza, J., Risueño, E., Tello, M.
26 Thermophysical characterization of Mg51%Zn eutectic metal alloy: A phase change
27 material for thermal energy storage in direct steam generation applications. Energy 72,
28 414-420, 2014.
- 29 26. Khare, S., Dell’Amico, M., Knight, C., McGarry, S. Selection of materials for high
30 temperature latent heat energy storage. Solar Energy Materials & Solar Cells 107, 20–27,
31 2012.
- 32 27. Petri, R.J., Ong, E.T. High temperature composite thermal energy storage (TES) Systems
33 for industrial applications. In: Proceedings of the 21st intersociety energy conversion
34 engineering conference 2, 873–880, 1986.
- 35 28. Kotzé, J.P., von Backström, T.W., Erens, P.J. High temperature thermal energy storage
36 utilizing metallic phase change materials and metallic heat transfer fluids. Journal of
37 Solar Energy Engineering ASME 135, 035001, 2013.

- 1 29. Li, F., Hu, Y., and Zhang, R., 2011, "The Influence of Heating-Cooling Cycles on the
2 Thermal Storage Performances of Al-17 Wt.% Si Alloy," *Adv. Mater. Res.*, 239–242, pp.
3 2248–2251.
- 4 30. Akiyama, T., Ashizawa, Y., Yagi, J. Storage and release of heat in a single spherical
5 capsule containing phase-change material with a high melting point. *Heat Transfer*
6 *Japanese Research* 21,199–217, 1992.
- 7 31. He, Qiao and Zhang, Wennan. A study on latent heat storage exchangers with the high-
8 temperature phase-change material. *International Journal of Energy Research* 25, 331-
9 341, 2001.
- 10 32. Kotzé, J.P., von Backström, T.W., Erens, P.J. Simulation and testing of a latent heat
11 thermal energy storage unit with metallic phase change material. *Energy Procedia* 49,
12 860-869, 2014.
- 13 33. Zhang, G., Li, J., Chen, Y., Xiang, H., Ma, B., Xu, Z., Ma, X. Encapsulation of copper-
14 based phase change materials for high Temperature thermal energy storage. *Solar Energy*
15 *Materials & Solar Cells* 128, 131-137, 2014.
- 16 34. Ma, B., Li, J., Xu, Z., Peng, Z. Fe-shell/Cu-core encapsulated metallic phase change
17 materials prepared by aerodynamic levitation method. *Applied Energy* 132, 568–574,
18 2014.
- 19 35. Andraka, C.E., Kruienza, A.M., Hernandez-Sanchez, B.A., Coker, E.N. Metallic Phase
20 Change Material Thermal Storage for Dish Stirling. *Energy Procedia* 69, 726-736, 2016.
- 21 36. He, Q., Zhang, W. A Study on Latent Heat Storage Exchangers With the High-
22 Temperature Phase-Change Material. *International Journal of Energy Research* 25, 331-
23 341, 2001.
- 24 37. Risueño, E., Doppiu, S., Rodríguez-Aseguinolaza, J., Blanco, P., Gil, A., Tello, M., Faik,
25 A., D'Aguanno, B. Experimental investigation of Mg-Zn-Al metal alloys for latent heat
26 storage application. *Journal of Alloys and Compounds* 685, 724-732,
- 27 38. Cottrell, A. An introduction to metallurgy. Edward Arnold Publisher (second edition),
28 ISBN: 0713125101, London, UK, 1975.
- 29 39. Chen, G. Ren, Z., Esfarjani, K. Metallic Composites Phase-Change Materials for High-
30 Temperature Thermal Energy Storage. SunShot conference (Department of Energy) 2013.
- 31 40. Fernandez, A.I., Martínez, M., Segarra, M., Martorell, I., Cabeza, L.F. Selection of
32 materials with potential in sensible thermal energy storage. *Solar Energy Materials &*
33 *Solar Cells* 94 (10), 1723-1729, 2010.
- 34 41. Ashby, M., Shercliff, H., Cebon, D. *Materials: engineering, science, processing and*
35 *design*. Elsevier Ltd., UK, 2007.

- 1 A. Risueño, E., Doppiu, S., Rodríguez-Aseguinolaza, J., Blanco, P., Gil, A., Tello, M.,
- 2 Faik, A., D'Aguanno, B. Experimental investigation of Mg-Zn-Al metal alloys for
- 3 latent heat storage application. *Journal of Alloys and Compounds* 685, 724-732, 2016.